



A novel mixed-ligand coordination polymer with pillared-layer & ladder like structure: synthesis, crystal structure, properties study, and application as sorbent for acetaminophen extraction

Mahmoud. Delavar^{1*}, Behnaz. Afzalian¹, Behrouz. Notash²

¹ Department of Chemistry, Payam Noor University (PNU), Tehran, Iran

² Department of Chemistry, Shahid Beheshti University, G.C., Evin, Tehran, Iran

*Corresponding author E-mail: delavar1392@gmail.com

Copyright © 2015 Mahmoud. Delavar et al. This is an open access article distributed under the [Creative Commons Attribution License](#), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Abstract

The novel coordination polymer, $[\text{Cd}(\text{NO}_3)_2(\text{P}-2)(\text{pzca})]_n$ (1); [P-2=pillar ligand = 4, 4'-bipyridine; pzca = 2-pyrazinecarboxylate] has been synthesized by the branched tube method under heat gradient condition and characterized by elemental analysis, FT-IR spectroscopy and powder X-ray diffraction. Compound 1 was structurally characterized by single-crystal X-ray diffraction. X-ray analysis reveals that it forms an one-dimensional covalent ladder like structure by two different bridging ligands, 4, 4'-bipy and pzca, which further significantly extends into two-dimensional networks via hydrogen bonding and other weak interactions. This polymer consists of three parts: equatorial layers, the bpy ligands connect axially these layers as the pillar which result in coordination pillared-layer structure (CPL) and one dimensional pores. The application of compound 1 was studied as a sorbent for extraction of acetaminophen medicine. Acetaminophen was extracted by solid phase extraction method and monitored by UV-Vis spectrophotometer. Furthermore, the remarkable thermal stability of compound 1 has also been studied by thermal gravimetric analyses (TGA).

Keywords: Coordination Polymer; Pillared-Layer Structures; Pillar Ligand; Acetaminophene; Solid Phase Extraction.

1. Introduction

Coordination polymers which build up with metal ions as connectors and organic bridging ligands as linkers have been extremely studied [1], [2]. These building-block units link to the metal centers via coordination bonds and other weak chemical interactions [3]. Design and synthesis of coordination polymers depend on their special properties and applications, such as: Molecular storage, luminescence, electrical conductivity, Sensor capability, and Catalysis [3], [5]. The synthesis methods are utilized for coordination polymer productions are generally the same as to grow any crystal. These, generally include solvent layering (slow diffusion), slow evaporation, slow cooling, hydro (solvo) thermal, microwave, ultrasonic, and solvent free method [6], [14].

Many significant properties of polymers depend principally on organic linkers. The connection mode and nature of the organic linkers with two or more donor atoms such as N, O, and/or S, perform very important roles to create the infinite structures of the coordination polymers. One of the useful organic linkers is 4, 4'-bipyridine (4, 4'-bpy) with N-containing heterocyclic moieties, which can act as a rigid, rodlike organic building block in the self-assembly of coordination frameworks. This ligand is well known as a pillar ligand in the CPL-n series and coordination polymers which are made up with this P ligand named CPL-2 structures. Kitagawa's group originally developed the CPL-n series and also were continued these studies by Kaneko et al [15], [16].

The coordination pillared-layer structures (CPLs), is one unique representative example of porous coordination polymers (PCPs) with high designability, regularity, and flexibility. The family of porous coordination polymers

(PCPs), which are division of “inorganic and organic hybrid polymers” are also called porous metal-organic frameworks (MOFs). The noticeable characteristics of CPLs are consequence of their potential applications in molecular storage, heterogeneous catalysis, drug delivery, and separation via sorption [17], [18].

One of the applications of separation procedure is extraction of the variety kind of medicine by MOFs structures, which are utilized as a sorbent such as polydimethylsiloxane (PDMS), polytetramethylesiloxane (PTMS), polytitania-tetramethylesiloxane [19], [20].

In this paper, we report a novel coordination pillared-layer structure; $[\text{Cd}(\text{NO}_3)(4, 4'\text{-bipy})(\text{pyzca})]_n$ 1; with anionic and neutral pillar mixed ligands, which is prepared by branched tube method [21]. In addition, Current research is also attracting attention towards the use of polymer as a sorbent for extraction and determination of medicine for the first time that have not reported before.

Acetaminophen medicine was extracted by solid phase extraction method (SPE). Acetaminophen (paracetamol, N-(4-hydroxyphenyl)acetamide, belongs to the most frequently used drugs worldwide. Acetaminophen is used as an analgesic and antipyretic agent. It is commonly used for the easement of fever, headache, and other minor aches and pains. Variety of analytical methods have been used for extraction of acetaminophen such as titrimetry, spectrophotometry, liquid chromatography, and electrochemical determination [22], [25] which consist of solid phase extraction, high pressure liquid chromatography, high-performance liquid chromatography, and Gas Chromatography-Mass Spectrometry [26], [28].

2. Experimental

2.1. Materials and instrumentation

$\text{Cd}(\text{NO}_3)_2 \cdot 3\text{H}_2\text{O}$, 2-pyrazinecarboxylic acids (Hpzca), 4, 4'-bipyridine (4, 4'-bipy) were purchased from Merck company. All solvent were of analytical grade and was used without further purification. Infrared measurements (KBr pellets) were carried out on a Shimadzu FT-IR spectrometer. Thermo-gravimetric analyses (TGA) were performed under air atmosphere with a heating rate of $10^\circ\text{C min}^{-1}$ using Shimadzu TGA-50 thermal analyses. Elemental analyses were carried out on a Thermo Finning Flash EA 1112 CHN elemental analyzer. X-ray powder diffraction (PXRD) measurements were performed with a Philips X'pert diffractometer. The extraction of medicine was detected by Shimadzu-2550 UV-Vis spectrophotometer.

2.2. Synthesis of $[\text{Cd}(\text{NO}_3)(4, 4'\text{-bipy})(\text{pyzca})]_n$ (1)

To isolate suitable single crystal of compound 1, $\text{Cd}(\text{NO}_3)_2 \cdot 3\text{H}_2\text{O}$ (one mmol, 0.308 g), Hpzca (one mmol, 0.241 g), bipy (1.5 mmol, 0.256 g) were placed in the main arm of a branched tube. MeOH was carefully added to fill both arms. The tube was sealed and immersed in an oil bath at 60°C while the other arm of the tube was kept at ambient temperature. After 1-2 days, colorless crystals were deposited in the branched arm. The crystals were isolated, filtered off, washed with acetone and ether and dried in air. Yield: 45.50%. Anal. Calcd for $\text{C}_{15}\text{H}_{11}\text{CdN}_5\text{O}_5$: C, 39.71; H, 2.44; N, 15.44. Found: C, 39.12; H, 2.56; N, 15.78. IR (cm^{-1}) selected bands: 432(w), 489(w), 628(m), 732(w), 806(m), 1018(w), 1045(w), 1072(w), 1157(w), 1218(w), 1384(vs), 1488(w), 1535(w), 1573(m), 1616(s), 3055(w), 3417(b).

2.3. Solid phase extraction of acetaminophen

Acetaminophen (10^{-3}M) was solved in H_2O (10 mL) and kept for 1hr in an ultrasonic bath. The coordination polymer (0.1 g) was added until the medicine solution and was sonicated for 30 minimums again. The sample was centrifuged subsequently at 3000 rpm for 10 minimums. After centrifuging, the initial solution and the solution after extraction were analyzed by UV-Vis spectrophotometer and confirmed the absorption of medicine.

2.4. X-ray crystal structure determination

The X-ray diffraction measurement was made on a STOE IPDS-II diffractometer with graphite monochromated Mo-K α radiation ($\lambda=0.71278 \text{ \AA}$). For $[\text{Cd}(\text{NO}_3)(4, 4'\text{-bipy})(\text{pyzca})]_n$ 1, colorless block shape, crystal was chosen, using a polarizing microscope which mounted on a glass fiber for data collection. Cell constants and orientation matrices for data collection were obtained by least-squares refinement of diffraction data from 4695 unique reflections. Data were collected to a maximum 2θ value of 58.5° in a series of ω scans in 1° oscillations and integrated using the Stoe X-Area [29] software package. The data were corrected for Lorentz and Polarizing effects. The structure was solved by direct methods [30] and subsequent difference Fourier maps and then refined on F2 by a full-matrix least-squares procedure, using anisotropic displacement parameters [31]. All aromatic hydrogen atoms were added in idealized positions. The atomic factors were taken from the International Tables for X-ray Crystallography [32]. All refinements were performed using the X-STEP32 crystallographic software package [33].

3. Results and discussion

One-dimensional pillared-layer ladder like structure of novel coordination polymer was synthesized by branched tube (hydrothermal) method. In this procedure, utilized the 4, 4'-bipy pillar ligand and pyrazinecarboxylate, result's mixed-ligand pillared-layer polymer. This structure was characterized by CHN analysis, TGA, PXRD and IR. The pillared-layer structure was utilized as a sorbent for extraction of acetaminophen. The extraction of acetaminophen was confirmed by UV-Vis spectrophotometer.

3.1. Crystallographic description of complexes

The single-crystal X-ray structural analysis reveals that the structure of compound 1 (Table 1) is a one-dimensional ladder like network based on binuclear cd block with mixed pyrazinecarboxylate anion, nitrate molecule and 4,4'-bpy. There is one crystallographically independent Cd(II) atom in the asymmetric unit of the coordination polymer which is coordinated to one oxygen and one nitrogen atom from one bidentate pzca ligand, one nitrogen atom from one 4,4'-bpy molecule and two oxygen atoms from one nitrate molecule (Fig. 1).

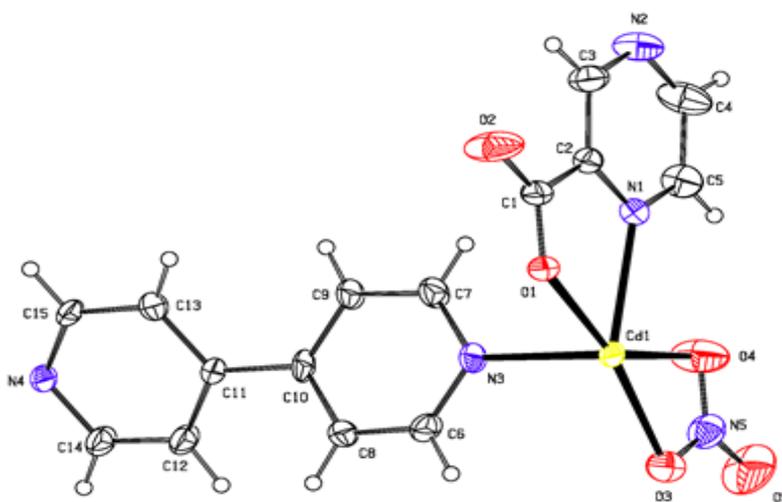


Fig. 1: ORTEP Diagram of the Asymmetric Unit of $[Cd(NO_3)(4,4\text{-bipy})(pzca)]_n$ Coordination Polymer. Thermal Ellipsoids are drawn at 30% Probability Level.

As it has shown in a view of the coordination sphere around Cd atoms in Fig. 2, each Cd (II) atom displays a seven-coordination number with pentagonal bipyramidal geometry by considering to connection of bridging oxygen atom (O1) of pzca from adjacent cd atom. As for the fundamental unit, Cd atom has six coordination numbers plus another one coordination number from bridging oxygen atom (O1) of adjacent chain ($Cd(1)-O_c(1) = 2.314 \text{ \AA}$).

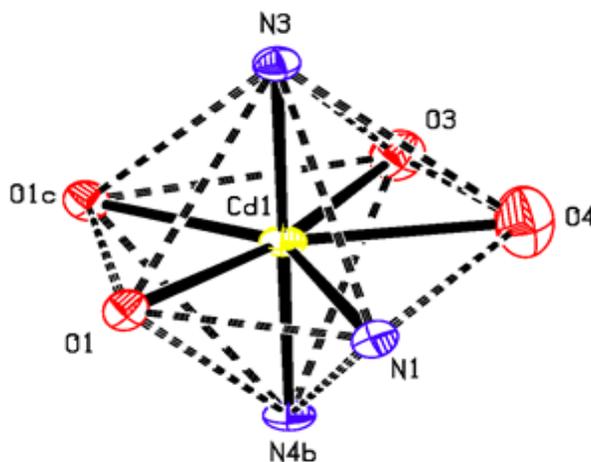


Fig. 2: View of the Coordination Sphere around Cd Atoms in $[Cd(NO_3)(4,4\text{-bipy})(pzca)]_n$ Coordination Polymer. Thermal Ellipsoids are drawn at 30% Probability Level.

The Cd(1) center coordinates to one oxygen atom ($Cd(1)-O1 = 2.383 \text{ \AA}$) and one nitrogen atom ($Cd(1)-N1 = 2.443 \text{ \AA}$) of one chelating carboxylate group, two oxygen atoms (O3, O4) of one nitrate molecule ($Cd(1)-O3 = 2.400 \text{ \AA}$, $Cd(1)-$

$O4 = 2.586 \text{ \AA}$), two nitrogen atoms ($Cd(1) - N(3) = 2.320 \text{ \AA}$, $Cd(1) - N(4) = 2.586 \text{ \AA}$) of different 4,4'-bpy ligands. The Cd–O bond distances are in the range of 2.383–2.586 \AA and the O–Cd (1)–O bond angles vary from 144.190 to 165.91 and the Cd–N distance are in the range of 2.320–2.443 \AA . Such two $\{CdN_3O_3\}$ pseudo octahedral are connected together to form a binuclear cd building unit via two bridging oxygen atom. Repeating of these connections results the one-dimensional ladder like structure, which is confirmed with crystal packing analysis (Fig. 3) [34].

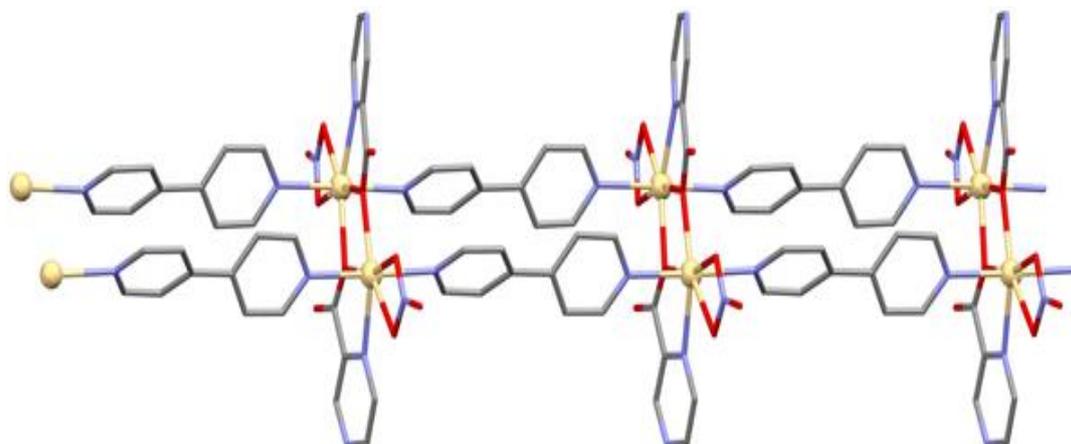


Fig. 3: Ladder-Like One-Dimensional Coordination Structure in $[Cd(NO_3)(4,4'\text{-bipy})(pzca)]_n$ Hydrogen Atoms Have Been Omitted for Clarity.

In this structure to each Cd atom connect one nitrate molecule and one pzca as a chelating agent at equatorial position, which result an equatorial plane. Furthermore, two equatorial plane of $[Cd(NO_3)(pzca)]$ connect together via two oxygen bridging atoms result the total equatorial layer in each unit (Fig. 4). The role of pillar ligand is connecting these equatorial layers to each other axially, which results pillared-layer structure (Fig. 5). One-dimensional parallel ladder like chains of polymer, connect to each other via hydrogen bonding and other weak interactions to result two-dimensional networks.

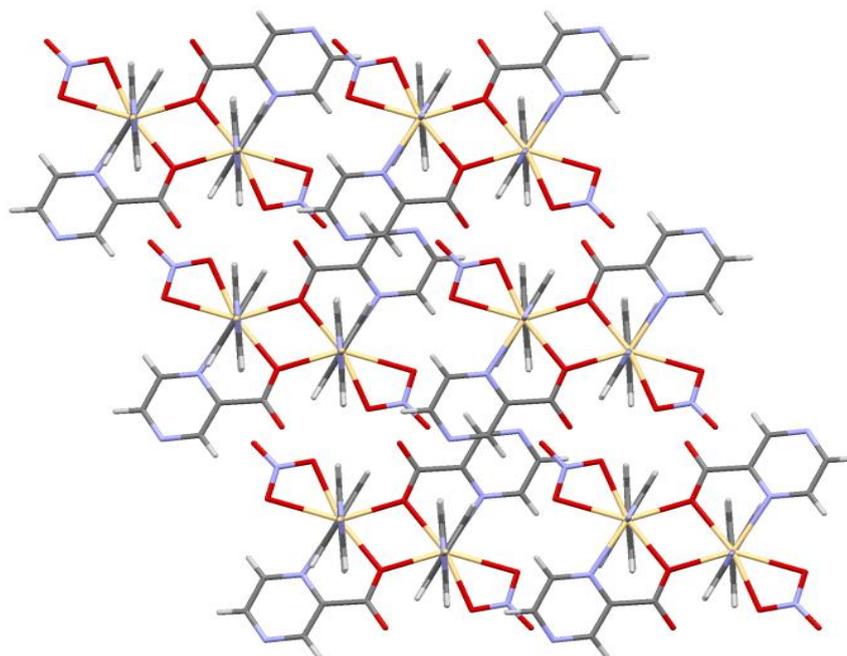


Fig. 4: Equatorial Layer of Compound 1 along C Axis.

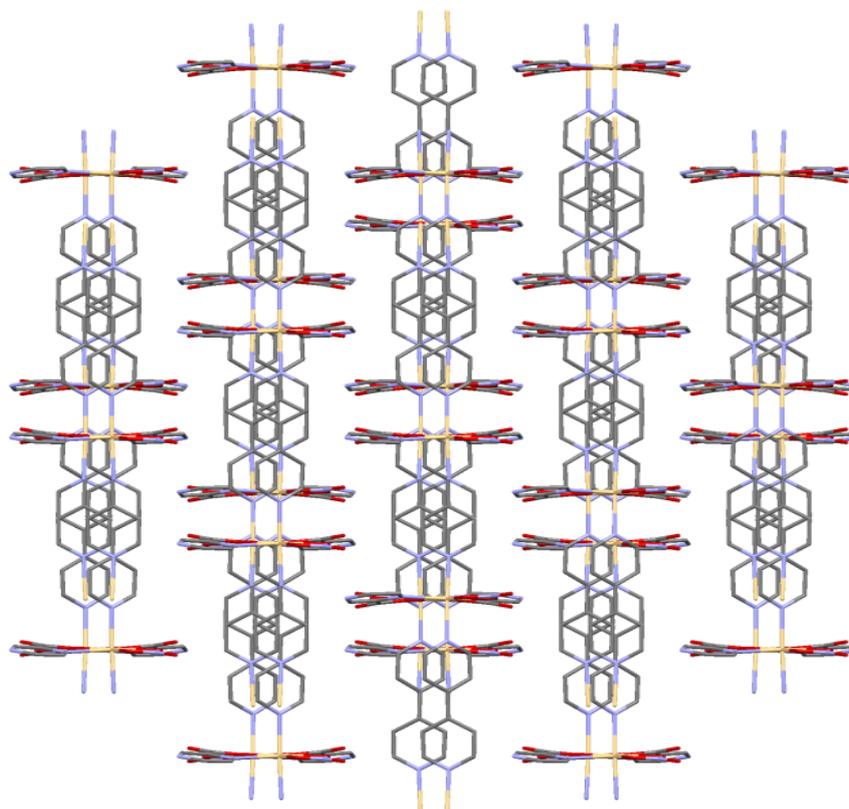


Fig. 5: Axial Pillar between Two Layers.

The crystal data and selected bond lengths and angles are listed in Table 1 and 2 which they are in good agreement with similar reports [35]. In the crystal structure of $[\text{Cd}(\text{NO}_3)(\text{bipy})(\text{pzca})]_n$, There are several C–H...N and C–H...O hydrogen bonding, which are listed in Table 3.

Table 1: Crystal Data for Coordination Polymer.

Complex	$[\text{Cd}(\text{NO}_3)(\text{bipy})(\text{pzca})]_n^a$
Empirical formula	C15H11N5O5Cd
Formula weight	453.70
Temperature (K)	298(2)
Wavelength (Å)	0.71069
Crystal system	Monoclinic
Space group	C2/c
a(Å)	16.797(3)
b(Å)	11.714(2)
c(Å)	19.632(4)
β (°)	114.86(3)
Volume (Å ³)	3504.9(14)
Z	8
Density (calculated) (g/cm ³)	1.720
Absorption coefficient (mm ⁻¹)	1.283
F(000)	1792
Crystal size (mm ³)	0.20 x 0.10 x 0.08
Theta range for data collection (°)	2.19–29.25
Reflections collected	12044
Independent reflections	4695 [Rint = 0.0740]
Absorption correction	Numerical
Maximum and minimum transmission	0.9043 and 0.7835
Data/restraints/parameters	4695 /0/235
Goodness-of-fit on F ²	0.856
R indices [I > 2σ(I)]	R1 = 0.0438, wR2 = 0.0635
R Indices (all data)	R1 = 0.1050, wR2 = 0.0733
Largest difference peak, hole (e Å ⁻³)	0.846 and -0.497

Table 2: Selected Bond Lengths (Å) and Angles (°) for Compound [Cd(NO₃)(bipy)(pzca)]_n^a.

Cd(1)-N(1)	2.443(3)	Cd(1)-O(1)#2	2.314(3)
Cd(1)-N(3)	2.320(3)	Cd(1)-N(4)#3	2.320(3)
Cd(1)-O(1)	2.383(3)	Cd(1)-O(3)	2.400(3)
Cd(1)-O(4)	2.586(4)	O(1)-Cd(1)#2	2.314(3)
N(4)-Cd(1)#1	2.320(3)	O(1)#2-Cd(1)-N(3)	88.89(13)
O(1)#2-Cd(1)-N(4)#3	90.20(13)	O(1)#2-Cd(1)-O(1)	71.87(9)
N(3)-Cd(1)-N(4)#3	178.09(12)	N(3)-Cd(1)-O(1)	88.44(14)
N(4)#3-Cd(1)-O(1)	92.88(14)	O(1)#2-Cd(1)-O(3)	94.06(10)
O(1)-Cd(1)-O(3)	165.91(9)	O(1)#2-Cd(1)-N(1)	139.43(11)
N(3)-Cd(1)-N(1)	92.46(13)	N(4)#3-Cd(1)-N(1)	89.32(13)
O(1)-Cd(1)-N(1)	67.64(10)	O(3)-Cd(1)-N(1)	126.44(11)
O(1)#2-Cd(1)-O(4)	144.19(10)	O(1)-Cd(1)-O(4)	143.93(9)

Asymmetry codes: #1: x, y-1, z; #2: -x, y, -z+3/2; #3: x, y+1, z.

Table 3: Geometrical Parameters of Hydrogen Bonds in [Cd(NO₃)(bipy)(pzca)]_n^a.

D-H...A	D-H/Å	H...A/Å	∠DHA/°	D...A/Å
C(15)-H(15)...N(2)#4	0.93	2.48	3.215(5)	130.7
C(12)-H(12)...O(3)#5	0.93	2.59	3.459(6)	154.9
C(12)-H(12)...O(2)#6	0.93	2.49	3.180(6)	130.8
C(5)-H(5)...O(4)	0.93	2.35	3.004(6)	127.2

Asymmetry codes: #4: -x+1/2, -y+3/2, -z+2; #5: -x-1/2, y-1/2, -z+3/2; #6: x-1/2, y-1/2, z.

3.2. FT-IR spectra

The most important IR frequencies attributed to the vibrations of free acid, 4,4'-bpy, and single crystal of compound 1 are reported in Table 4. The weak bands at 848 cm⁻¹ for Hpzca, 815 and 786 cm⁻¹ for 4,4'-bpy, and 848 and 794 cm⁻¹ for the compound 1, result from the aromatic skeleton vibrations of the pyrazine and pyridine rings. Some moderately and weak intense bands appeared in the 400–500 cm⁻¹ region are assigned to new ν (M–N) and ν (M–O) (M = Cd) bands, which further suggest bond formation between the metal and N- and O- donors of the ligand [36].

Table 4: Important FT-IR Data for Nano-Sized, Single Crystal of Complex 1, Hpzca and 4, 4'-bpy (Cm⁻¹).

	ν(C—H)	ν(COOH)	ν(C—C)	vas(C=O)	vs(C=O)	ν(C—O)	ν(M–O)	ν(M–N)
4,4'-bpy	3024	—	1485	—	—	—	—	—
Hpzca	3062	1720	1460	—	—	1049	—	—
crystal compound 1	3055	—	1488	1616	1384	1045	563	432-489

The IR spectra of compound one displays a band at 1616 cm⁻¹ which is attributed to the asymmetric stretching vibration of C=O group of pzca and the bands at 1384 and 1350 cm⁻¹ refer to symmetric stretching vibration of carboxyl group, respectively[37]. The separation [vas (COO-) – vs (COO-)] for compound 1 (232 cm⁻¹) indicating that the COO - of pzca coordinated to Cd in a mono dentate mode [38]. Therefore, the absence bands in the region 1690–1730 cm⁻¹ was indicated complete deprotonation of Hpzca molecule. The wave number separation [vas (N-O) – vs (N-O)] Indicating that coordinated nitrate group is in a chelating mode which can be proved by their crystal structural determination [39]. These data Cd atoms was coordinated to ligands through nitrogen and oxygen of the heterocyclic.

3.3. Thermal analysis

The thermal gravimetric analysis of [Cd(NO₃)(bipy)(pzca)]_n, were carried out between 30-800 °C under air atmosphere, (Fig. 6). The TGA curve of compound 1 displayed three decomposition steps that occurred at 42.13 °C, 150-400 °C and 400-550 °C respectively. The first decomposition step was released ca. 2.41 wt % of its mass at seven minimums with the rate mass loss about 0.014 mg/min. The second decomposition step at 150-400 °C lost ca. 43.69 wt % at 25 min with rate mass loss about 0.07 mg/min. The final decomposition occurred between 400-550 °C with a mass loss of 25.85% at 15 min with rate mass loss about 0.07 mg/min. Total decomposition which is between 30-550 °C, was 4.216 mg (71.67%) due to the loss of ligand species. Decomposition was completed at 460 °C and the mass loss calculations showed that the final decomposition product was CdO. This curve played that compound 1 is air stable and has high thermal stability upper than 300 °C.

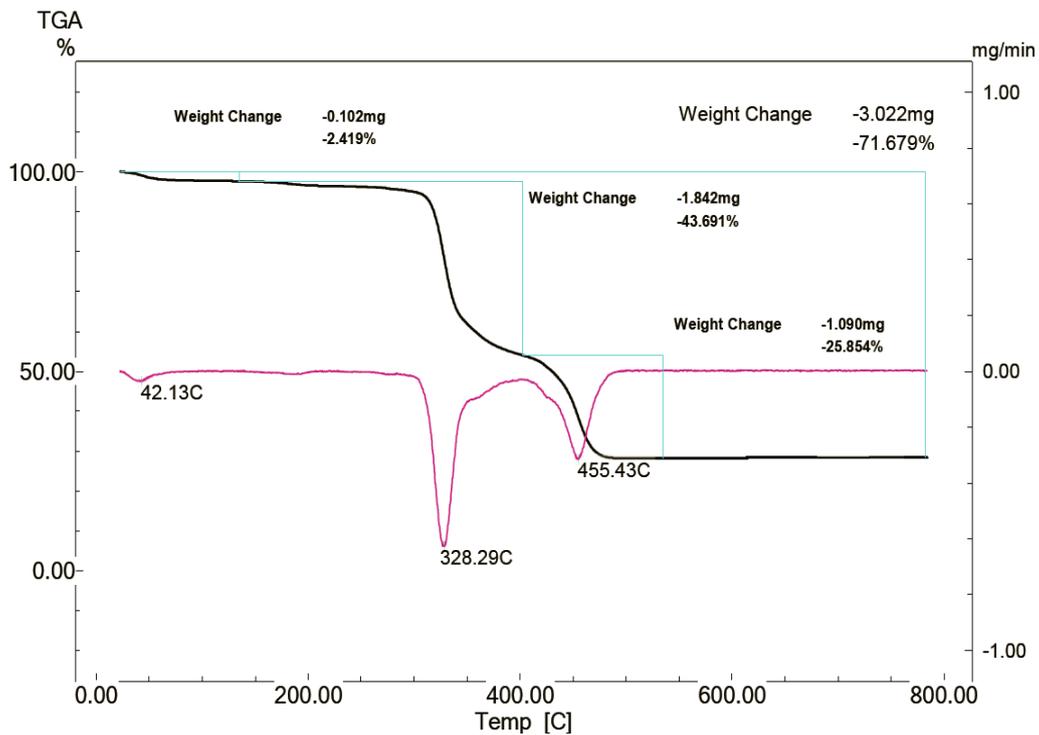


Fig. 6: The TGA of Single Crystal of Compound 1.

3.4. X-ray diffraction

PXRD measurement was performed on the compound 1 prepared to utilize the hydrothermal methods (Fig. 7). The observed PXRD patterns are also in agreement with the simulated ones from the single-crystal diffraction data.

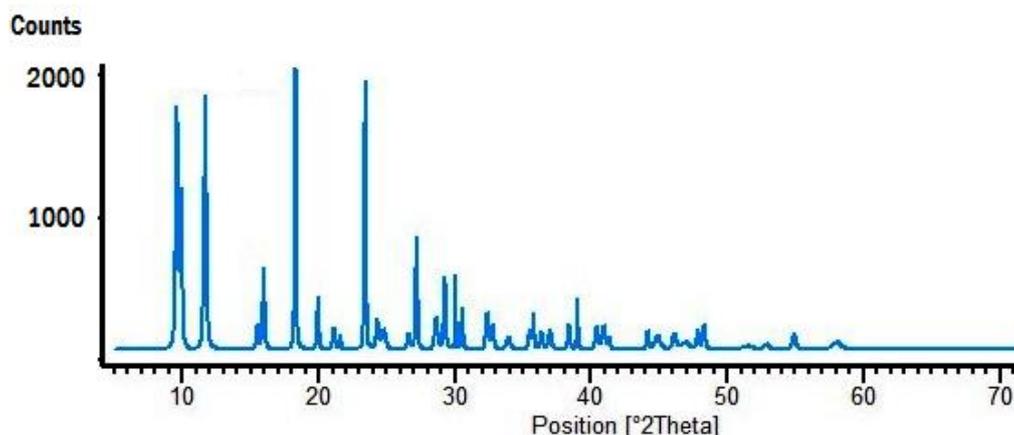


Fig. 7: This Is the XRD Pattern of Compound 1.

3.5. Extraction analysis

The aim of this report is the development a simple and sensitive UV-Vis spectrophotometer method for separation and quantifying of acetaminophen medicine (Fig. 8).




Fig. 8: The Structure of Acetaminophen (Paracetamol).

The utilized method in our extraction procedure is simple, sensitive, and time consuming without using a lot of solvents can be applied for determination of each drug. Coordination polymer as a sorbent showed the highest efficiency in extraction of acetaminophen and UV-Vis spectrophotometer confirmed the results. For extraction, the compound 1 as a sorbent was immersed into the sample solution and then acetaminophen molecules travel from the donor phase to the extractor phase. The absorption spectra was recorded using a UV-Visible spectrophotometer. Signals were monitored at 254-257 nm. The separation of acetaminophen medicine before, and after extraction is represented in Fig. 9.

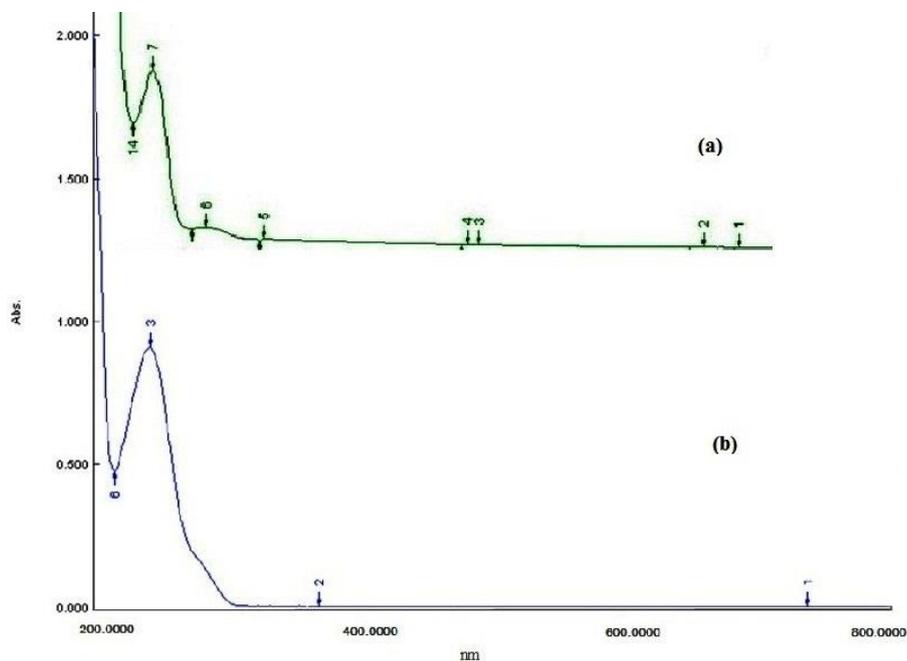


Fig. 9: The UV-Vis Spectrum (A) Before Extraction, (B) after Extraction of Acetaminophen

The polymer structure plays the main role of this extraction as a porous solid phase for adsorption of medicine. This structure has one-dimensional channel pores that result of distance between bipy ligands at two adjacent chains, but by considering to hydrogen bonding and resulting a supramolecular network, we observe new added one-dimensional channels in the structure which is made of interaction between two adjacent ladder chain (Fig. 10). Presence of these channels, hydrogen bonding, and other weak interactions between the structure of medicine and the structure of polymer caused to efficiency extraction of acetaminophen. Another advantage is determination of trace amount of medicine by simple method and inexpensive equipment at low time.

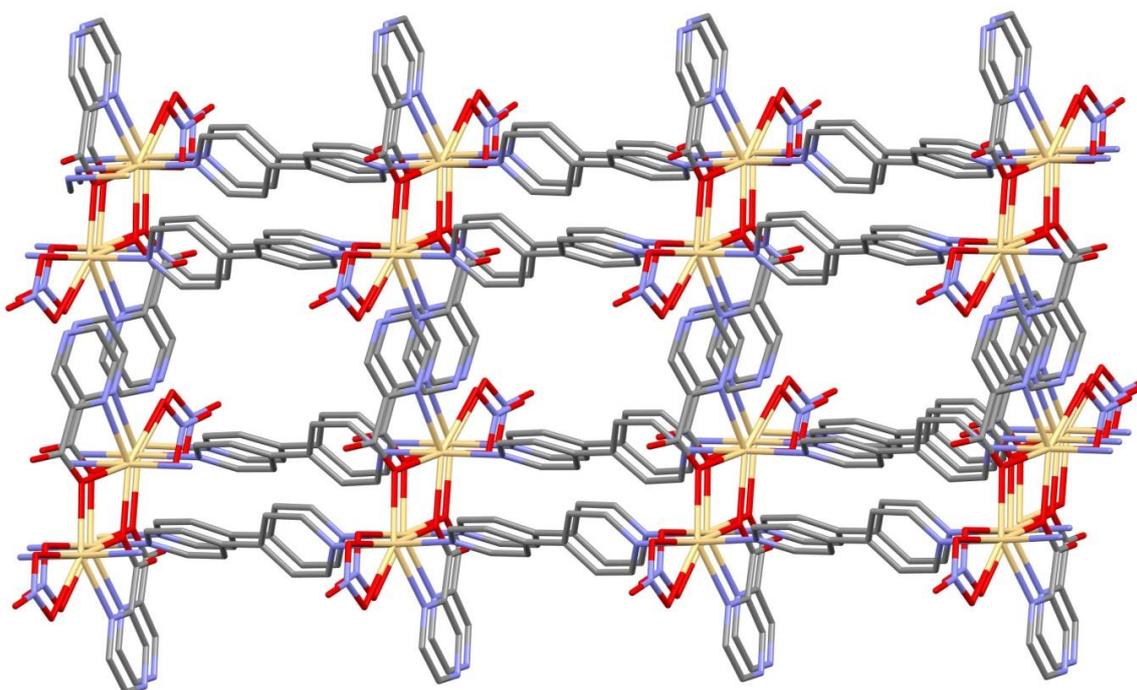


Fig. 10: One-Dimensional Channel Pores of Compound 1.

4. Conclusion

In this paper, we describe a simple synthetic preparation of a novel coordination polymer. This method for preparation of coordination polymers has some advantages such as: taking places in shorter reaction times, producing better yields, producing the single crystal at high quality. The structure of polymer was confirmed by thermal stability, PXRD, FT-IR, and elemental analysis. This polymer was utilized as a sorbent for extraction of acetaminophen medicine. One of the advantages of this study is utilizing the coordination polymer as sorbent for extraction of acetaminophen medicine by the time-consuming and simple method. Furthermore, monitoring and determination of trace amount of medicine by UV-Vis spectrophotometer as inexpensive equipment is another benefit which we reach to it.

5. Supplementary data

CCDC 933939 contains the supplementary crystallographic data for compound 1. These data can be obtained free of charge via <http://www.ccdc.cam.ac.uk/conts/retrieving.html>, or from the Cambridge Crystallographic Data Centre, 12 Union Road, Cambridge CB2 1EZ, UK; fax: (+44) 1223-336-033; or e-mail:deposit@ccdc.cam.ac.uk.

Acknowledgements

The authors are thankful to the Chemistry Department of the Payam Noor and Shahid Beheshti University.

References

- [1] M.G. Amiri, A. Morsali, A.D. Hunter, M. Zeller, Spectroscopy, thermal and structural studies of new ZnII coordination polymer, [Zn₃ (m-bpa) 4.5 (AcO) 3] (ClO₄)₃·4.26H₂O, *Solid State. Sci*, 9 (2007) 1079-1084. <http://dx.doi.org/10.1016/j.solidstatesciences.2007.07.016>.
- [2] S.I. Noro, S. Kitagawa, T. Akutagawa, T. Nakamura, Coordination Polymers constructed from transition metal ions and organic N-containing heterocyclic ligands: Crystal structures and microporous properties, *Prog. Polym. Sci*, 34 (2009) 240-279. <http://dx.doi.org/10.1016/j.progpolymsci.2008.09.002>.
- [3] L. Hashemi, A. M orsali, Sonichemical Synthesis of a New Ethylene Diamine Lead(II) Coordination Polymer as Precursor for Preparation of PbO Nano-Structure *Cryst. Eng. Commun*, 14 (2012) 779. <http://dx.doi.org/10.1039/C2CE06133C>.
- [4] F. Jing Liu, D. Sun, H. Jun Hao, R.B. Huang, L.S. Zheng, Anion-controlled assembly of silver (I)/amonobenzonitrile compounds: syntheses, crystal structure, and photolumenecence properties, *Cryst. Growth. Des*, 12 (2012) 354. <http://dx.doi.org/10.1021/cg201159z>.
- [5] A. Erxleben, "Structures and properties of Zn (II) coordination polymers", *Coord. Chem. Rev*, 246 (2003) 203. [http://dx.doi.org/10.1016/S0010-8545\(03\)00117-6](http://dx.doi.org/10.1016/S0010-8545(03)00117-6).
- [6] M. Oh, C.A. Mirkin, Chemically tailorable colloidal particles from infinite coordination polymers. *Nature*, 438 (2005) 65. <http://dx.doi.org/10.1038/nature04191>.
- [7] Y.-M. Jeon, G.S. Armatas, D. Kim, M.G. Kanatzidis, C.A. Mirkin, Tröger's-base-derived infinite coordination polymer microparticles, *Small*, 5 46 (2009). <http://dx.doi.org/10.1002/sml.200801160>.
- [8] P.J. Hagrman, D. Hagrman, J. Zubiet, Organic-inorganic hybrid materials: from "Simple" coordination polymers to organodiamine-templated molybdenum oxides, *Angew. Chem. Int. Ed*, 38 (1999) 2638-2648. [http://dx.doi.org/10.1002/\(SICI\)1521-3773\(19990917\)38:18<2638::AID-ANIE2638>3.0.CO;2-4](http://dx.doi.org/10.1002/(SICI)1521-3773(19990917)38:18<2638::AID-ANIE2638>3.0.CO;2-4).
- [9] X.M. Chem, M.L. Tong, Solvothermal in Situ Metal/Ligand Reactions: A New Bridge between Coordination Chemistry and Organic Synthetic Chemistry *Acc. Chem. Res*, 40 (2007) 162-170. <http://dx.doi.org/10.1021/ar068084p>.
- [10] J.H. Liao, P.L. Chen, C.C. Hsu, "Syntheses and structure characterization of inorganic/organic coordination polymers: Ag (dpa), Co (O3PH) (4, 4 '-bpy) (H₂O), Zn (O3PH) (4, 4 '-bpy) (0.5) and Mn [O2PH (C6H5)] (2), *J. Phys. Chem. Slids*, 62 (2001) 1629-1642. [http://dx.doi.org/10.1016/S0022-3697\(01\)00101-9](http://dx.doi.org/10.1016/S0022-3697(01)00101-9).
- [11] S. Kitagawa, T. Okubo, S. Kawata, M. Kondo, M. Katada, H. Kobayashi, An oxalate-linked copper (II) coordination polymer, [Cu₂ (oxalate) 2 (pyrazine) 3] n, constructed with two different copper units: X-ray crystallographic and electronic structures, *Inorg. Chem*, 34 (1995) 4790-4796. <http://dx.doi.org/10.1021/ic00123a012>.
- [12] J.M.J. Paulusse, J.P.J. Huijbers, R.P. Sijbesma, Quantification of Ultrasound-Induced Chain Scission in PdII-Phosphine Coordination Polymers, *Chem. Eur. J*, 12, (2006) 4928-4934. <http://dx.doi.org/10.1002/chem.200600120>.
- [13] J.M.J. Paulusse, R.P. Sijbesm, Reversible mechanochemistry of a PdII coordination polymer *Angew. Chem. Int. Ed*, 34 (2004) 4560-4562. <http://dx.doi.org/10.1002/ange.200460040>.
- [14] V.P. Balema, J.W. Wiench, M. Pruski, V.K. Pecharsky, Solvent-free mechanochemical synthesis of two Pt complexes: cis-(Ph₃P)PtCl₂ and cis-(Ph₃P)PtCO₃, *Chem. Commun*, (2002) 1606-1607. <http://dx.doi.org/10.1039/b203694k>.
- [15] X. Xu, X. Liu, X. Zhang, T. Sun, Synthesis, characterization and property study of new coordination polymers constructed from flexible dicarboxylates and bidentate nitrogen mixed ligands *Solid State Sci*, 12 (2010) 355-360. <http://dx.doi.org/10.1016/j.solidstatesciences.2009.11.013>.
- [16] O.J. Garcí'a-Ricard, A.J. Herná'ndez-Maldonado, Cu₂ (pyrazine-2, 3-dicarboxylate) 2 (4, 4'-bipyridine) Porous Coordination Sorbents: Activation Temperature, Textural Properties, and CO₂ Adsorption at Low Pressure Range *J. Phys. Chem C*, 114 (2010) 1827-1834.
- [17] A. Kondo, T. Daimaru, H. Noguchi, T. Ohba, K. Kaneko, H. Kanoh, Adsorption of water on three-dimensional pillared-layer metal organic frameworks, *J. Colloid Interface Sci*, 314 (2007) 422. <http://dx.doi.org/10.1016/j.jcis.2007.05.090>.
- [18] M. Eddaoudi, J. Kim, N. Rosi, D. Vodak, J. Wachter, M. O'Keeffe, O.M. Yaghi, Systematic design of pore size and functionality in isoreticular MOFs and their application in methane storage, *Science*, 295 (2002) 469. <http://dx.doi.org/10.1126/science.1067208>.
- [19] S. Bureekaew, S. Shimomura, S. Kitagawa, Chemistry and application of flexible porous coordination polymers, *Sci. Technol. Adv. Mater*, 9 (2008) 014108. <http://dx.doi.org/10.1088/1468-6996/9/1/014108>.
- [20] C. Bicchi, C. Cordero, P. Rubiolo, P. Sandra, Impact of water/PDMS phase ratio, volume of PDMS, and sampling time on Stir Bar Sorptive Extraction (SBSE) recovery of some pesticides with different KO/W, *J. Sep. Sci*, 26 (2003) 1650. <http://dx.doi.org/10.1002/jssc.200301613>.

- [21] A. Morsali, M.Y. Masoom, Structures and properties of mercury (II) coordination polymers, *Coord. Chem. Rev.*, 253 (2009) 1882–1905. <http://dx.doi.org/10.1016/j.ccr.2009.02.018>.
- [22] G. Burgot, F. Auffret, J.L. Burgot, Determination of acetaminophen by thermometric titrimetry, *Anal. Chim. Acta*, 343 (1997) 125–128. [http://dx.doi.org/10.1016/S0003-2670\(96\)00613-7](http://dx.doi.org/10.1016/S0003-2670(96)00613-7).
- [23] A.B. Moreira, H.P.M. Oliveira, T.D.Z. Atvars, I.L.T. Dias, G.O. Neto, E.A.G. Zagatto, L.T. Kubota, Direct determination of paracetamol in powdered pharmaceutical samples by fluorescence spectroscopy, *Anal. Chim. Acta*, 539 (2005) 257–261 [24] C. Nebot, S.W. Gibb, K.G. Boyd, *Anal. Chim. Acta*, 598 (2007) 87–94.
- [24] X. Chen, J. Zhu, Q. Xi, W. Yang, A high performance electrochemical sensor for acetaminophen based on single-walled carbon nanotube-graphene nanosheet hybrid films, *Sens. Actuators B*, 161 (2012) 648–654. <http://dx.doi.org/10.1016/j.snb.2011.10.085>.
- [25] D.J. Speed, S.J. Dickson, E.R. Cairns, N.D. Kim, Analysis of paracetamol using solid-phase extraction, duterated internal standards, and gas chromatography–mass spectrometry, *J. Anal. Toxicol.*, 25 (2001) 198–202. <http://dx.doi.org/10.1093/jat/25.3.198>.
- [26] R.A. Horvitz, P.I. Jatiow, Determination of Acetaminophen concentration in serum by high-pressure liquid chromatography, *CLIN. CHEM.*, 23/9 (1977) 1596–1598.
- [27] S.G. Nelson, Z. Wan, M.A. Stan, SN2 Ring Opening of β -Lactones: An Alternative to Catalytic Asymmetric Conjugate Additions, *J. Org. Chem.*, 67 (2002) 4680–4683. <http://dx.doi.org/10.1021/jo025519n>.
- [28] Stoe&Cie, X–AREA: *Program for the Acquisition and Analysis of Data*, (Version 1.30), Stoe&Cie GmbH: Darmstadt, Germany (2005).
- [29] G. M. Sheldrick. *SHELX 97. Program for Crystal Structure Solution*, University of Göttingen, Germany (1997).
- [30] G. M. Sheldrick. *SHELX 97. Program for Crystal Structure Refinement*, University of Göttingen, Germany (1997).
- [31] A.J.C. Wilson (Ed.). *International Tables for X-ray Crystallography*, Vol. C, Kluwer Academic Publisher, Dordrecht, Netherlands (1995).
- [32] Stoe&Cie, X-STEP32: *Crystallographic Package*, (Version 1.07b), Stoe&Cie GmbH: Darmstadt, Germany (2000).
- [33] A.Y. Robin, K.M. Fromm, Coordination polymer networks with O- and N-donors: What they are, why and how they are made, *Coord. Chem. Rev.*, 250 (2006) 2127–2157. <http://dx.doi.org/10.1016/j.ccr.2006.02.013>.
- [34] J.-H. Liao, C.-Y. Lai, C.-D. Ho, C.-T. Su, Syntheses and characterization of two coordination polymers: [Cd(isonicotinate)₂(H₂O)] DMF and Cd₃(isonicotinate)₄(NO₃)₂(4,4'-bipy)₂(H₂O)₂ *Inorg. Chem. Commun.*, 7 (2004) 402–404. <http://dx.doi.org/10.1016/j.inoche.2003.12.012>.
- [35] P. Chutia, Sh. Kato, T. Kojima, Sh. Satokawa, Synthesis and characterization of Co(II) and Cu(II) supported complexes of 2-pyrazinecarboxylic acid for cyclohexene oxidation, *Polyhedron*, 28 (2009) 370–380. <http://dx.doi.org/10.1016/j.poly.2008.10.063>.
- [36] Y.-C. Liang, M.-C. Hong, J.-C. Liu, R. C. Hydrothermal syntheses, structural characterizations and magnetic properties of cobalt (II) and manganese (II) coordination polymeric complexes containing pyrazinecarboxylate ligand, *Inorg. Chim. Act.*, 328 (2002) 152–158. [http://dx.doi.org/10.1016/S0020-1693\(01\)00716-2](http://dx.doi.org/10.1016/S0020-1693(01)00716-2).
- [37] F. Zhang, L. Hao, L. Zhang, X. Zhang, Solid-State Thermolysis Preparation of Co₃O₄ Nano/Micro Superstructures From Metal-Organic Framework for Supercapacitors, *Int. J. Electrochem. Sci.*, 6 (2011) 2943–2954.
- [38] M. Sun, P. Wang, H. Zhou, J. Yang, J. Wu, Y. Tian, X. Tao, M. Jiang, 1D chain Cd(II) and Co(II) coordination polymers: Synthesis, crystal structures and luminescence properties *J. Mol. Struct.*, 873 (2008) 73–78. <http://dx.doi.org/10.1016/j.molstruc.2007.03.019>.