

Economic Machining of Hardened Steels by Hard Turning and its Process Variables

Abhishek Anand¹, Ajay Kumar Behera^{2*}, Sudhansu Ranjan Das³

^{1,2*}Siksha O Anusadhan, Deemed to be University, Bhubaneswar, Odisha, India

³VSSUT Burla, Sambalpur, Odisha, India

*Corresponding author E-mail: ajaybehera@soauniversity.ac.in

Abstract

Hard turning has evolved as an important machining technique for cutting of hardened steel. In the recent past, increasing use of hard turning in automotive sector has been observed. Hard turning is greatly affected by factors like machine tool, tool geometry, cutting tool materials, cutting parameters, and lubrication as well as cooling methods. This paper presents all the factors that influences hard turning operations performance and is an attempt to give a proper understanding of the process. This paper further discuss, in brief, about cylindrical grinding and its comparison with hard turning, which confirms the elimination of long technological chain of traditional production process by implementing hard turning with appropriate selection of abovementioned process variables.

Keywords: Hard turning, Grinding, Machine tool, Cutting tool, Cooling techniques, Cutting parameters

1. Introduction

The primary aim for any manufacture is to produce product of high quality with reduced machining time and cost in order to sustain in this competitive machining industries. But the traditional machining operations involve expensive machinery, long manufacturing cycle and more setup time. Today's hardened high-surface steel parts are becoming increasingly important in many engineering applications because of the increasing challenge along with necessity and use of high precision parts to acquire critical performances and due to their excellent essential qualities (high indentation resistance, high value of hardness-to-modulus of elasticity ratio, low ductility with high abrasiveness) and in particular, these are truly hard-to-cut materials [1]. Traditional method of machining hardened steels involve an expensive and time-consuming technological chain of operations. In this way, machining operations need to continually adopt newer, more efficient and cost-effective manufacturing approaches to assess the machining of difficult as well as hard-to-cut materials. In recent past, hard turning has emerged as solution to overcome these problems of traditional machining operations. Hard turning is a machining process to machine material having hardness value greater than 45 HRC which presents embryonic benefits as well as interests in preference to conventional cylindrical grinding; (1) by without losing the product quality in connection with more flexible, less expensive and more eco-friendly production, and (2) by employing appropriate and very hard futuristic tool materials under critical machining condition. Considerable reduction of long-established old machining operation involving forming, annealing, rough turning, heat treatment and finish grinding illustrated in Figure

1a, abbreviation of production cycles and costs, less energy consumption & setup time (refer, Fig. 1b), superior process flexibility, improvement of productivity and surface integrity by eliminating the risk of cutting fluid through environment friendly finish dry cutting, which is considered in turning of hard material, have established a superior advantage of a mechanism from the economical, technological, and environmental point of views [2,3]. Figure 2 illustrates the economic benefits of production process of hardened steel components, when the process is changing from grinding to hard turning. Hard turning was developed in early eighties. Machining of hardened steel, by hard turning was earlier used in automotive industries for manufacturing of transmission components. Because of wear resistance & improved strength of hardened steel, it has a huge demand in gear-shafts, bearings, machine tools, camshafts, punch and die manufacturing [6]. Tools that are commonly used in hard turning are cubic boron nitride (CBN), PCBN, ceramics and carbides. A lot of research work is done on hard turning suggests that under suitable condition, hard turning can produce components with great dimensional accuracy and better surface finish. In terms of performance, properly configured machine tool can produce a hard turned part with a surface finish of $0.4\mu\text{m}$, diameter tolerance of $\pm 3-7\mu\text{m}$ and size control of the range of $2-5\mu\text{m}$ [7]. Since hard turning is usually performed dry, i.e. without the use of any coolant, it not only reduces the cost of production but also reduces environmental pollution [8]. Also, machining center used in hard turning consumes less electricity when compared with grinding machine, hence reducing the cost of production. In hard turning, chips can easily be recycled, whereas in grinding operation, the sludge produced needs a costly separation process. Material removal rate is 4-6 times higher in hard turning when compared with grinding process, also there is reduction in the

machining time to about 60% in this process [9] and especially, when employed for machining complex contours, it can reduce the manufacturing cost can be reduced to about 30% as mentioned by Huang et al. [10]. A qualitative overview is shown in Figure 3.

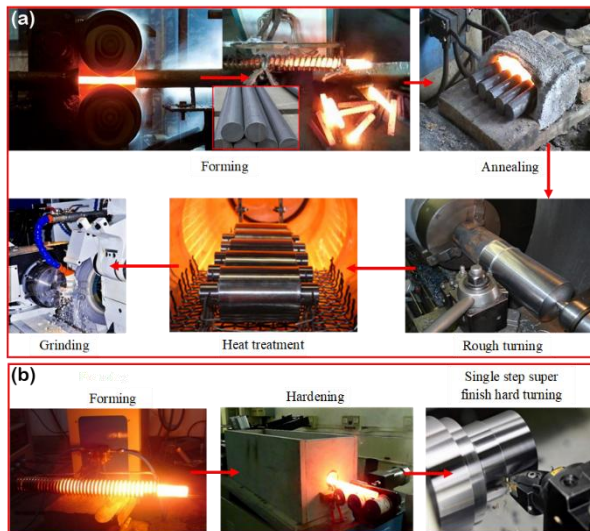


Figure 1: (a) Technological chain for conventional production process, and (b) hard turning production [4]



Figure 2: Economic benefits of hard turning [5]

Hard turning was developed in early eighties. Machining of hardened steel, by hard turning was earlier used in automotive industries for manufacturing of transmission components. Because of wear resistance & improved strength of hardened steel, it has a huge demand in gear-shafts, bearings, machine tools, camshafts, punch and die manufacturing [6]. Tools that are commonly used in hard turning are cubic boron nitride (CBN), PCBN, ceramics and carbides. A lot of research work is done on hard turning suggests that under suitable condition, hard turning can produce components with great dimensional accuracy and better surface finish. In terms of performance, properly configured machine tool can produce a hard turned part with a surface finish of $0.4\mu\text{m}$, diameter tolerance of $\pm 3-7\mu\text{m}$ and size control of the range of $2-5\mu\text{m}$ [7]. Since hard turning is usually performed dry, i.e. without the use of any coolant, it not only reduces the cost of production but also reduces environmental pollution [8]. Also, machining center used in hard turning consumes less electricity when compared with grinding machine, hence reducing the cost of production. In hard turning, chips can easily be recycled, whereas in grinding operation, the sludge produced needs a costly separation process. Material removal rate is 4-6 times higher in hard turning when compared with grinding process, also there is reduction in the machining time to about 60% in this process [9] and especially, when employed for machining

complex contours, it can reduce the manufacturing cost can be reduced to about 30% as mentioned by Huang et al. [10]. A qualitative overview is shown in Figure 3.

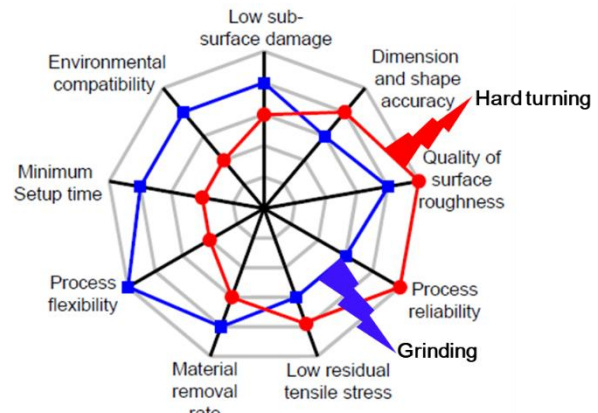


Figure 3: Qualitative overview of the capability of hard turning and grinding processes [11]

2. Process Variables in Hard Turning

Hard turning process is dependent on machine technology, process technology, materials and tooling technology, cutting technology, and work-holding technology. The key change drivers in the case of hard turning are consisting of various machining process variables, shown in Figure 4. In order to replace cylindrical grinding, the following factors should be considered for successful hard turning which are associated with the machining parameters: (1) a machine with a high dynamic stiffness, (2) proper work holding devices, (3) a correctly chosen cutting tools and advanced insert materials, (4) high quality cutting edges, (5) rigid tool mounts, (6) appropriate machining parameters, (7) component part rigidity, and (8) chip management and cooling system.

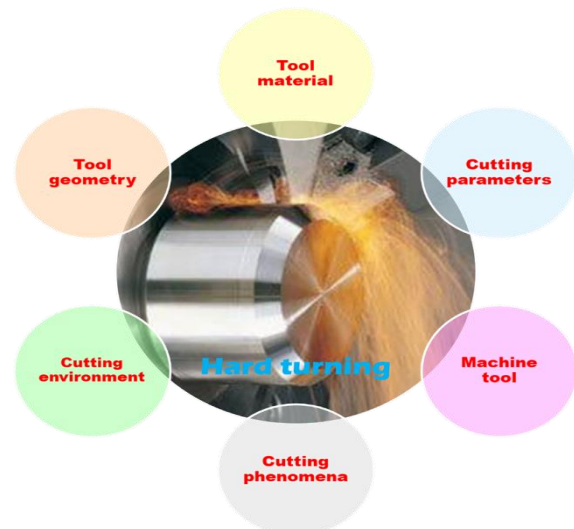


Figure 4: Influence of different parameters on hard turning

2.1 Machine Tool

Hard turning differs from other conventional machining as it involves the machining of hard material having hardness greater than 45HRC. A high surface speed of 250 mm/min or even more than that can be achieved in this turning process, so there is a need of proper

machine tool rigidity, high surface speed along with constant surface speed for profile to be finished [12]. The surface finish, size control and tool life are hugely affected by the dynamic stiffness of machine tool. So any improvement in dynamic stiffness of machine tool will lead to; (a) less operating vibration, (b) considerably improved tool life, (c) considerably improved part quality, (d) higher through-put, and (e) minimum machining parameter adjustments [9]. Large dynamic thrust force is generated while machining of hard material. For this, various machine tool attributes should be consider in the machining system for the production of critically hard finished steel component, which are illustrated in Fig. 5. Therefore, hard turning cannot be performed on all conventional machine setup as the above mentioned requirement must be fulfilled for hard turning. Type of structure material greatly influences material removal rate of machine tool, accuracy, and total cost. Common material used for machine tool are cast iron and steel, although granite and epoxy concrete have been developed and used for structures.

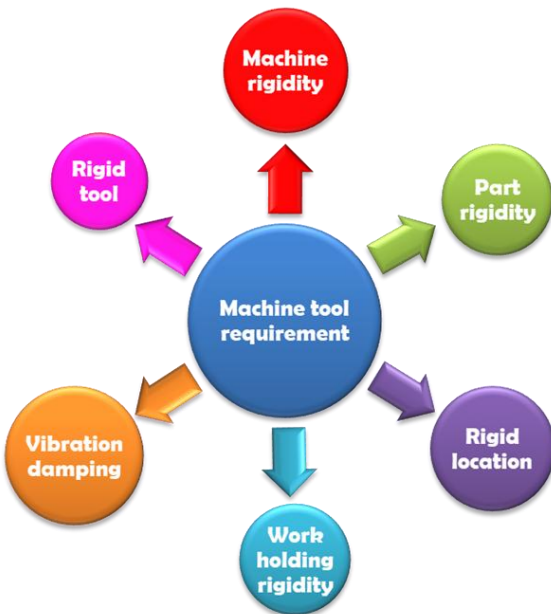


Figure 5: Machine tool requirements in hard turning process

2.2 Cutting Tool for Hard Turning

Although hard turning technology is effective and competitive than grinding process with respect to cost, time and environment yet it encounters problems because of uncertainties related to tool wear pattern, and tool life prediction. So there is a need for suitable cutting tool material with low wearing capabilities as high cutting force is generated. Wide variety of super hard advanced tool materials are used for hard turning, such as cubic boron nitride (CBN), mixed ceramic and coated carbide offer manufactures an attractive replacement for traditional grinding to machine hardened steel. Of the above mentioned tool, most commonly used tool for machining, CBN has a great demand in metalworking industries to machine hardened steel [13], since it is one of the hardest known material and retains its hardness even at high temperature. In comparison to other tools like ceramic or carbide, CBN generally have more wear resistance and shows chemical stability at elevated temperature and also, exhibits properties like high coefficient of thermal conductivity as well as thermal resistance [14]. However, high fabrication & material cost of CBN and rapid tool wear has led to the development of tool material that can overcome these problems.

2.3 Tool Geometry for Hard Turning

Tool geometry is an influencing factor that affects the hard turning operation. Parameters like surface finish, tool wear, heat generation (produced by cutting temperature), chip formation and cutting force are greatly affected by the tool geometry, as demonstrated in Figure 6. The cutting edge & alignment of the tool face are most important geometric parameters for chip formation. Tool material used for turning have large hardness value and are brittle. They are also prone to fracture. There is generation of high temperature and force for cutting in hard turning. To overcome these problems, cutting tool is provided with negative rake angle, but if this rake angles value is increased, then it gives rise to high compressive stress [15].

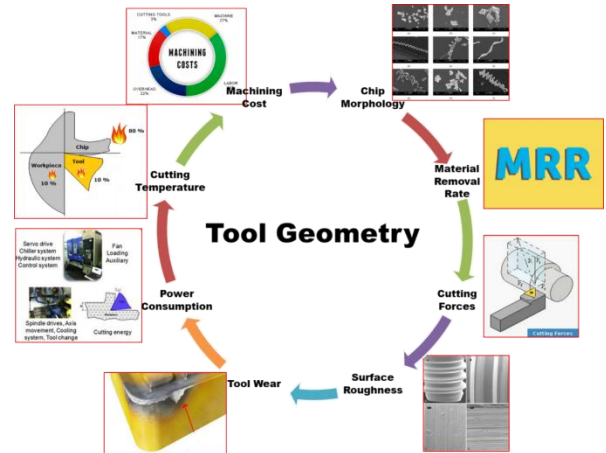


Figure 6: Technological response parameters affected by tool geometry

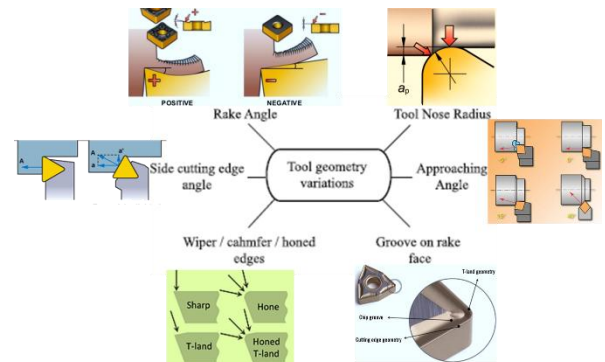


Figure 7: Illustrations of tool geometry

Selective research works have been performed to understand the impact of tool geometry design and in its influence to performance in hard turning, as shown in Table 1(a). Cutting process is greatly affected by tool's cutting edge angle. This is because, for a given feed and depth of cut, cutting edge angle defines the uncut thickness, width of cut and hence the life of tool [7]. Proper tool nose radius improves the machinability by increasing the tool life, as it can reduce the temperature generation at tool's tip and also increase surface finish, and it also increase strength and cutting edge's life without significant increase in the cutting force [16]. An experimental study investigate the impact of rake angle, entering angle of cutting tool and cutting velocity on machining force and temperature at tools tip[17]. Edge hone radius also effect the machining in hard turning as surface roughness is directly proportional to edge hone radius. Thrust force is also affected by edge hone radius. When compared to chamfered edge, the force were smaller in small hone radius [18]. Cutting force and tool life are greatly affected by chamfer angle. With increase in chamfer

angle, force in cutting also increases. Another study suggests that in order to get maximum tool life, chamfer angle should be 15° [19].

Table 1: Overview of various work and cutting tool materials along with machining process variables for hard turning

(a) Tool geometry for hard turning					
Author	Workpiece material and hardness	Cutting tool	Cutting parameters	Tool geometry	Machining characteristic(s)
Guddat et al. [20]	AISI 52100 (58-62HRC)	PCBN	Cutting speed, depth of cut and feed rate	Insert type, nose radius, edge radius, chamfer angle	Surface integrity
Davoudinejad&Nordin [21]	DF-3 tool steel (58HRC)	PVD-TiN coated mixed ceramic insert	Cutting speed, tool length, feed	Chamfered, honed edge geometry	Tool wear, tool life, cutting forces, surface integrity
Anthony [22]	AISI D2 (55HRC)	Multicoated carbide, cermet, ceramic inserts	Cutting velocity, depth of cut and feed rate	Nose radius, clearance angle, rake angle	Cutting force, chip morphology
Zerti et al. [23]	AISI D3	Mixed ceramic tool	Cutting velocity, depth of cut, feed rate	Nose radius, major cutting edge angle	Surface finish, tangential force, specific cutting force, cutting power
Aouici et al. [24]	AISI H11 (50HRC)	Coated and uncoated ceramic tool	Cutting velocity, depth of cut, feed	Nose radius	Cutting forces
(b) Lubrication & cooling techniques for hard turning operation					
Author	Workpiece material and hardness	Cutting tool	Cutting parameters	Lubrication/Cooling techniques	Machining characteristic(s)
Paul and Varadarajan [27]	AISI 4340 (46HRC)	Multilayer coated carbide insert	Cutting speed, feed	minimal fluid application	tool vibration, cutting force, temperature, surface finish, wear

Sahu et al. [31]	AISI 1015 (43HRC)	Carbide insert	Cutting velocity, depth of cut, feed rate	spray impingement cooling & dry environment	in tool surface roughness, cutting temperature, material removal rate
Mia and Dhar [32]	AISI 1060 (40-56HRC)	Coated carbide tool	Cutting speed, feed	Dry, high pressure coolant system	Surface roughness, cutting temperature
Nouioua et al. [33]	X210Cr12 steel	Multilayer coated carbide insert	Cutting velocity, depth of cut, feed rate, nose radius	dry, wet, minimum quantity lubrication	Surface roughness, cutting force
Kaynak and Gharibi [34]	AISI 4140 (42HRC)	Carbide insert	Cutting velocity, depth of cut, feed rate	MQL, cryogenic cooling	Wear in tool

2.4 Cutting Fluid & Lubrication Techniques

Hardened steel is generally machined dry condition in turning operation. Dry cutting produces smoother surface finish as the heat produced in the cutting zone can make shearing easy by reducing the shear strength of the work piece. It can result in improved surface finish [25]. Also the absence of lubricants and fluids reduce cost of machining and also protects labor and environment. However, due to the tool and work piece friction in hard turning, heat is generated in the cutting zone that can cause effect life of tool, and also increases the thermal damage of the work piece. Reduced tool life can add to the cost of production. Cutting fluid reduces the cutting force, hence reducing the energy consumption and also helps to cool the cutting area and hence increase tool life. Currently, application of cutting fluids by different cooling and lubricating methods have made tremendous effort to improve the efficacy as well as cutting performance of hard turning process, as in Fig 8. However, the application of cutting fluid is restricted because it adversely affect the environment. The problem of cutting fluid can be reduced by using solid lubricants in machining, cryogenic cooling by liquid nitrogen and minimum quantity lubrication (MQL). The solid lubricant, molybdenum di-sulphite (MoS_2) assisted hard turning reduces surface roughness and also reduces cutting force as compared dry hard turning condition, but do not greatly affect tool life and wear [26]. Another experiment with minimal fluid application in presence of grease and 10% graphite resulted in improved cutting performance when compared to dry turning and turning with minimal fluid application [27]. In a study with synthetic oil having 6% of conc. in water, it was found that cutting in dry environment requires less power and gives better surface finish compared to wet cutting [28]. In an experiment, Minimum quantity lubrication (MQL) with vegetable oil, it was concluded that machining with Minimum quantity lubrication produces improved result than in dry machining as the wear of tool is reduced and also improves tool life [29]. In comparison to MQL assisted hard turning,

it was found that there was 23.52% reduction in cutting temperature in minimal cutting fluid application (MCFA). Also it is more environment friendly. Machining can also be performed by replacing conventional fluids with cryogenics such as liquid nitrogen or solid carbon dioxide. Hard turning with cryogenics (i.e. cryogenic machining) helps to remove heat during cutting at a faster rate, which helps to increase tool life and also improves the surface finish [30]. Cryogenic cooling can be performed in three ways. One way is by cryogenic pre-cooling of the work piece, where work piece is cooled before machining. In second way, cooling is performed without the direct contact of cryogenic on work piece or tool. The third way is by cryogenic spraying at the cutting zone to remove generated heat.

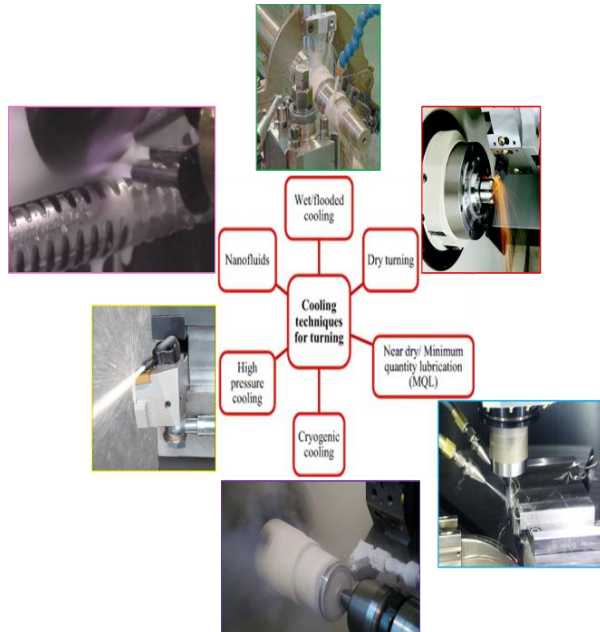


Figure 8: Cooling techniques in turning hard steel

3. Cutting Parameters

Performance of hard turning is greatly influenced by the parameters, i.e., cutting velocity, feed rate and depth of cut. Various researchers performed hard turning operation to predict machinability on different hardened steels by varying cutting parameters. The purpose of the investigation reported in Suresh and Basavarajappa [35] was to reveal the impact of process parameters: depth of cut, velocity and axial feed rate on flank wear of coated ceramic tool and surface finish of hardened AISI H13 steel (55 HRC) by conducting the dry turning experiment in CNC lathe. The results indicated that cutting speed predominantly affects tool wear while feed is high influencing factor in surface finish. Rashid et al. [36] revealed that lower feed produces improved machined surface finish, but causes high tool wear, so the choice of a suitable feed must be determined by trade-off between the quality and cost consideration. In a study, Bensouilah et al. [37] observed that growth of surface roughness and cutting force components substantially affected because of cutting parameters namely cutting velocity and feed. During hard turning of AISI D3 steel with uncoated (CC650) and coated (CC6050) ceramic inserts. Regardless, the development of flank wear for both cutting tools within control limit $VB = 0.3$ mm, surface finish of the machined part was better i.e. did not exceeded $1.6 \mu\text{m}$ (as good as manufactured by grinding), but better surface is improved by coated ceramic tool when differentiated to the surface developed by the uncoated ceramic. In an experiment on AISI 52100 steel with CBN

tool, it shows that cutting force is directly proportional to feed rate and depth of cut, while decreases with cutting speed. Cutting force was mostly influenced by depth of cut followed by feed and cutting velocity [38]. The higher cutting force at a lower cutting velocity is because of low temperature and formation of built up edge. As cutting velocity increases, flank wear of the tool is also increased leading to immediate deterioration machine surface quality. Surface roughness is greatly influenced by feed as it increases with increase in feed, followed by cutting velocity, whereas depth of cut has negligible impact on surface roughness [39].

4. Conclusions

The overview presented in this paper is a collective work on machining and machinability improvement of hardened steels by hard turning which is being adopted successfully in automotive and mold as well as die making industries. A worthy attention related to hard turning was surveyed in an attempt to find the achievable part quality and techno-economic efficiency of hard turning process in comparison with grinding on the basis of varying machine tool, tool geometry and material, cutting parameters and cooling methods. After reviewing a long string of literatures, following conclusions were reported,

- Large dynamic thrust force is generated while machining of hard material. Therefore, the machine tool associated with following attributes like rigid tool, part rigidity, rigid location, high surface speed etc. should be consider in the machining system which are beneficial for hard turning.
- In complex hard turning process, large volume of heat is generated due to vibration and exhaustive involvement of heavy mechanical load as well as high temperature on cutting tool, therefore ultra-super hard materials such as ceramic and coated carbide tools are useful for hard turning from technological point-of-view, but in most of the cases, CBN tools are used to machine hardened steel as they have high hardness, coefficient of thermal conductivity and thermal resistance.
- Tool geometry has significant effect on improvement of finish hard turning. As the nose radius increases, improved surface roughness is achieved. With increase in edge hone radius and chamfer angle, cutting force also increases.
- Dry cutting technique is used in hard turning which results the process to be economical and also environment friendly. It can be concluded form the recent studies that use of high-pressure coolant system, cryogenic cooling and MQL can improve the performance in hard turning operation by enhancing the tool life.
- When compared with grinding, hard turning is techno-economical because of low setup time, faster cycle time and has a higher material removal rate.

To meet the rapidly growing demands not only for increasing productivity, quality and economy of conventional materials but also for satisfactory machining of exotic materials, environment friendliness and ultra-precision finishing lot of possibilities are rapidly generated and remarkable improvements and use of novel but simple techniques and technologies are coming up.

References

- [1] K. Nakayama, M. Arai, and T. Kanda, "Machining characteristics of hard materials", *CIRP Annals-Manufacturing Technology*, Vol. 37, No. 1, pp. 89–92, (1988).
- [2] H. Tonshoff, C. Arendt, and R.B. Amor, "Cutting of hardened steel", *CIRP Annals-Manufacturing Technology*, Vol. 49, No. 2, pp. 547–566, (2000).

- [3] W. Grzesik, "Machining of hard materials, In: J. Paulo Davim (ed.), *Machining Fundamentals and Recent Advances*", Springer-Verlag, London, pp. 97-126, (2008).
- [4] A. Panda, S.R. Das, D. Dhupal, "Surface Roughness Analysis for Economical Feasibility Study of Coated Ceramic Tool in Hard Turning Operation", *Process Integration and Optimization for Sustainability*, Vol. 1, No. 4, pp. 237-249, (2017).
- [5] Stefan G Larsson, "Hard Turning Economics" Technical report. Seco Tool Advanced Material Expert.
- [6] Chinchanihar, S., & Choudhury, S. K. (2015). Machining of hardened steel—Experimental investigations, performance modeling and cooling techniques: A review. *International Journal of Machine Tools and Manufacture*, 89, 95–109.
- [7] V.P. Astakhov, "Machining of Hard Materials –Definitions and Industrial Applications" In: J. Paulo Davim (ed.), *Machining of Hard Materials*", Springer-Verlag, London, pp. 1-32, (2011).
- [8] Benedicto, E., Carou, D., & Rubio, E. M. (2017). Technical, Economic and Environmental Review of the Lubrication/Cooling Systems Used in Machining Processes. *Procedia Engineering*, 184, 99–116.
- [9] "Fundamentals of hard turning", GOSIGER. <https://www.gosiger.com>
- [10] Huang, Y., Chou, Y. K., & Liang, S. Y. (2006). CBN tool wear in hard turning: a survey on research progresses. *The International Journal of Advanced Manufacturing Technology*, 35(5-6), 443–453.
- [11] F. Klocke, E. Brinskmeier, and K. Weinert, "Capability profile of hard cutting and grinding processes", *CIRP Annals-Manufacturing Technology*, Vol. 54, No. 2, pp. 22–45, (2005).
- [12] Bartarya, G., & Choudhury, S. K. (2012). State of the art in hard turning. *International Journal of Machine Tools and Manufacture*, 53(1), 1–14.
- [13] Aouici, H., Yallese, M. A., Chaoui, K., Mabrouki, T., & Rigal, J.-F. (2012). Analysis of surface roughness and cutting force components in hard turning with CBN tool: Prediction model and cutting conditions optimization. *Measurement*, 45(3), 344–353.
- [14] Ali Hosseini and Hossam A. Kishawy, "Cutting Tool Materials and Tool Wear" In: J. Paulo Davim (ed.), *Machining of Titanium Alloys*", Springer-Verlag Berlin Heidelberg, pp. 31-56, (2014).
- [15] Dogra, M., Sharma, V.S. and Dureja, J. (2011) 'Effect of tool geometry variation on finish turning – a review', *Journal of Engineering Science and Technology Review*, Vol. 4, No. 1, pp.1–13.
- [16] Zhao, T., Zhou, J. M., Bushlya, V., & Ståhl, J. E. (2017). Effect of cutting edge radius on surface roughness and tool wear in hard turning of AISI 52100 steel. *The International Journal of Advanced Manufacturing Technology*, 91(9-12), 3611–3618.
- [17] Saglam, H., Yaldiz, S., & Unsacar, F. (2007). The effect of tool geometry and cutting speed on main cutting force and tool tip temperature. *Materials & Design*, 28(1), 101–111.
- [18] Endres, W.J. and Kountanya, R.K. (2002) 'The effects of corner radius and edge radius on tool flank wear', *Journal of Manufacturing Processes*, Vol. 4, No. 2, pp.89–96.
- [19] Zhou, J.M., Walter, H., Andersson, M. and Stahl, J.E. (2003) 'Effect of chamfer angle on wear of PCBN cutting tool', *International Journal of Machine Tools Manufacture*, Vol. 43, No. 3, pp.301–305.
- [20] Guddat, J., M'Saoubi, R., Alm, P., & Meyer, D. (2011). Hard turning of AISI 52100 using PCBN wiper geometry inserts and the resulting surface integrity. *Procedia Engineering*, 19, 118–124.
- [21] Davoudinejad, A., & Noordin, M. Y. (2014). Effect of cutting edge preparation on tool performance in hard-turning of DF-3 tool steel with ceramic tools. *Journal of Mechanical Science and Technology*, 28(11), 4727–4736.
- [22] X. M. Anthony, Analysis of cutting force and chip morphology during hard turning of AISI D2 steel. *Journal of Engineering Science and Technology*, Vol. 10, No. 3 (2015) 282 – 290.
- [23] Zerti, O., Yallese, M. A., Khettabi, R., Chaoui, K., & Mabrouki, T. (2016). Design optimization for minimum technological parameters when dry turning of AISI D3 steel using Taguchi method. *The International Journal of Advanced Manufacturing Technology*, 89(5-8), 1915–1934.
- [24] Aouici, H., Khellaf, A., Smaiah, S., Elbah, M., Fnides, B., & Yallese, M. A. (2017). Comparative assessment of coated and uncoated ceramic tools on cutting force components and tool wear in hard turning of AISI H11 steel using Taguchi plan and RMS. *Sādhanā*, 42(12), 2157–2170.
- [25] Mia, M., & Dhar, N. R. (2017). Prediction and optimization by using SVR, RSM and GA in hard turning of tempered AISI 1060 steel under effective cooling condition. *Neural Computing and Applications*. doi:10.1007/s00521-017-3192-4.
- [26] Singh, D. and Venkateswara Rao, P. (2008) 'Performance improvement of hard turning with solid lubricants', *International Journal of Advance Manufacturing Technology*, Vol. 38, Nos. 5–6, pp.529–535.
- [27] Paul, S.P., Varadarajan, AS. (2012), 'Performance evaluation of hard turning of AISI 4340 steel with minimal fluid application in the presence of semi-solid lubricants', *Proceedings of the Institution of Mechanical Engineers, Part J: Journal of Engineering Tribology*, Vol 227, Issue 7, pp. 738 – 748.
- [28] Diniz, A.E., Ferreira, J.R. and Filho, F.T. (2003) 'Influence of refrigeration/lubrication condition on SAE 52100 hardened steel turning at several cutting speeds', *International Journal of Machine Tools and manufacturing*, Vol. 43, No. 3, pp.317–326.
- [29] Mia, M., Dey, P. R., Hossain, M. S., Arafat, M. T., Asaduzzaman, M., ShoriatUllah, M., & TareqZobaer, S. M. (2018). Taguchi S/N based optimization of machining parameters for surface roughness, tool wear and material removal rate in hard turning under MQL cutting condition. *Measurement*, 122, 380–391.
- [30] Leadebal Jr, W. V., de Melo, A. C. A., de Oliveira, A. J., & Castro, N. A. (2018). Effects of cryogenic cooling on the surface integrity in hard turning of AISI D6 steel. *Journal of the Brazilian Society of Mechanical Sciences and Engineering*, 40(1). doi:10.1007/s40430-017-0922-6.
- [31] Sahu, S. K., Mishra, P. C., Orra, K., & Sahoo, A. K. (2014). Performance assessment in hard turning of AISI 1015 steel under spray impingement cooling and dry environment. *Proceedings of the Institution of Mechanical Engineers, Part B: Journal of Engineering Manufacture*, 229(2), 251–265.
- [32] Mia, M., & Dhar, N. R. (2016). Optimization of surface roughness and cutting temperature in high-pressure coolant-assisted hard turning using Taguchi method. *The International Journal of Advanced Manufacturing Technology*, 88(1-4), 739–753.
- [33] Nouioua, M., Yallese, M. A., Khettabi, R., Belhadi, S., Bouhalais, M. L., & Girardin, F. (2017). Investigation of the performance of the MQL, dry, and wet turning by response surface methodology (RSM) and artificial neural network (ANN). *The International Journal of Advanced Manufacturing Technology*, 93(5-8), 2485–2504.
- [34] Kaynak, Y., & Gharibi, A. (2018). Progressive Tool Wear in Cryogenic Machining: The Effect of Liquid Nitrogen and Carbon Dioxide. *Journal of Manufacturing and Materials Processing*, 2(2), 31.
- [35] Suresh R, Basavarajappa S. Effect of Process Parameters on Tool Wear and Surface Roughness during Turning of Hardened Steel with Coated Ceramic Tool. *Procedia Materials Science* 2014; 5: 1450–1459.
- [36] Rashid W Bin, Goel S, Davim JP, Joshi SN. Parametric design optimization of hard turning of AISI 4340 steel (69 HRC). *International Journal of Advanced Manufacturing Technology* 2016; 82: 451–462.
- [37] Bensouilah H, Aouici H, Meddour I, Athmane M. Performance of coated and uncoated mixed ceramic tools in hard turning process. *Measurement* 2016; 82:1–18.
- [38] Bouacha, K., Yallese, M. A., Mabrouki, T., & Rigal, J.-F. (2010). Statistical analysis of surface roughness and cutting forces using response surface methodology in hard turning of AISI 52100 bearing steel with CBN tool. *International Journal of Refractory Metals and Hard Materials*, 28(3), 349–361.
- [39] S.R. Das, A. Kumar, and D. Dhupal, "Experimental investigation on cutting force and surface roughness in machining of hardened AISI 52100 steel using cBN tool", *International Journal of Machining and Machinability of Materials*, Vol. 18, No. 5, pp. 501-521, (2016).